

# Bioengineering Functional Copolymers. XX. Synthesis of Novel Anticancer Active Poly(maleic anhydride-*alt*-2-vinyl-1,3-dioxolane) and its Organoboron Amide-Ester Branched Derivatives Biyomühendislik Fonksiyonel Kopolimerleri. XX. Yeni Antikanser Aktif Poli(maleik anhidrid-*alt*-2-vinil-1,3-dioxolan) ve Organoboron Amid-Ester Dallanmış Türevleri

Research Article

**Gülten Kahraman,<sup>1</sup> Mustafa Türk,<sup>2</sup> Zakir M. O. Rzayev,<sup>3\*</sup> Ernur A. Söylemez,<sup>3</sup> Serpil Oğuztüzün<sup>2</sup>**

<sup>1</sup>Turkish Atomic Energy Authority (TAEK), Sarayköy Nuclear Research and Training Center, Ankara, Turkey

<sup>2</sup>Kırıkkale University, Department of Biology, Faculty of Arts and Sciences, Yahşihan, Kırıkkale, Turkey

<sup>3</sup>Hacettepe University, Division of Nanotechnology and Nanomedicine, Institute of Science and Engineering, Ankara, Turkey

## ABSTRACT

Novel bioengineering alternating copolymer and its organoboron amide and  $\alpha$ -hydroxy- $\omega$ -methoxypoly(ethylene oxide) (PEO) branched derivatives were synthesized by (1) complex-radical alternating copolymerization of two non-homopolymerizable in chosen reaction conditions monomers such as maleic anhydride (MA) and 2-vinyl-1,3-dioxolane (VDO), (2) amidolysis of synthesized poly(MA-*alt*-VDO) with 2-aminoethyl-diphenylboronate and (3) esterification-grafting of organoboron copolymer with PEO. The complex-formation ( $K_c$ ) and the monomer reactivity ratios ( $r_1$  and  $r_2$  copolymerization constants), structure and composition of the synthesized copolymers were characterized by chemical (alkali titration), FTIR-ATR and NMR spectroscopy, TGA-DSC thermal analysis methods. Cytotoxicity found as having an order as organoboron branched PEO copolymer < poly(MA-*alt*-VDO) < organoboron copolymer of these novel copolymers containing a combination of ionizable, hydrophilic/hydrophobic, organoboron, carboxyl-amide-ester-ether groups, toward HeLa cells was investigated.

### Key Words

Synthesis, Alternating copolymer, Amidolysis, Esterification, Organoboron copolymer, Cytotoxicity, HeLa cells.

## ÖZET

Yeni biyomühendislik alternatif kopolimerinin ve organobor amid ve  $\alpha$ -hidroksi- $\omega$ -metoksi-poli(etilen oksit) (PEO) ile dallanmış türevlerinin sentezi, (1) Seçilen reaksiyon şartlarında homopolimerleşmeyen maleik anhidriti (MA) ve 2-vinil-1,3-dioksolan (VDO) monomerlerinin kompleks-radikal alternatif kopolimerizasyonu, (2) sentezlenen poli(MA-*alt*-VDO) makromoleküllerinin 2-amino-etildifenilboronat ile amidolizi ve (3) PEO ile esterleşmesi yöntemleri kullanarak gerçekleştirilmiştir. Monomerlerin kompleks oluşumu ( $K_c$ ) ve kopolimerleşme sabitleri ( $r_1$  ve  $r_2$ ), çok fonksiyonel gruplar içeren kopolimerlerin yapısı, içeriği ve ısıl özellikleri kimyasal analiz (alkali titrasyon), FTIR-ATR and NMR spektroskopisi ve TGA-DSC ile karakterize edilmiştir. İyonize olabilen, hidrofilik/hidrofobik, organobor, anhidrit-karboksil-amid-ester-eter gibi gruplar içeren bu kopolimerlerin HeLa hücrelerine sitotoksik etkisi araştırılmış ve organobor-PEO kopolimer < poli(MA-*alt*-VDO) < organobor kopolimer sırasında olduğu belirlenmiştir.

### Anahtar Kelimeler

Sentez, Alternatif kopolimer, Amidoliz, Esterleşme, Organobor kopolimer, Sitotoksiste, HeLa hücreleri.

**Article History:** Received September 29, 2011; Revised January 12, 2012; Accepted February 11, 2012; Available Online: April 30, 2012.

**Correspondence to:** Zakir M. O. Rzayev, Hacettepe University, Institute of Science & Engineering, Division of Nanotechnology and Nanomedicine, Beytepe, 06800 Ankara, Turkey

Tel: +90 312 297 64 39

Fax: +90 312 299 21 24

E-Mail: zmo@hacettepe.edu.tr


## INTRODUCTION

Alternating copolymers of alkyl vinyl ethers with maleic anhydride (MA) have received significant attention because of their unique properties and wide range of applications such as adhesives, photocrosslinkable and photosetting resin compositions, photographic films, electrophotographic recording and glass fiber coatings, reversible shear thinning gels, detergents, viscosity improvers, flocculants, and cellular plastics (only *tert*-butyl derivative), as well as controlled-release coatings, medicinal tablet coatings, animal antidiarrhea capsules, and so forth. Methyl vinyl and divinyl ether copolymers, show antitumor activity and the property of induced production of interferon in animals, which is potentially useful for inhibiting the growth of Friends leukemia virus [1,2]. The alternating copolymerization of unsaturated cyclic ethers, such as *p*-dioxene [3-5], 2,3-dihydro-2H-pyran (DHP) [6] and 4-glycidyl-2,3-dihydro-2H-pyran [7] as the electron-donor monomers with MA as the electron-acceptor monomer was a subject of early publications of Iwatsuki and Yamashita, Fujimori and Rzaev et al., respectively. Han et al. [8,9] have reported the synthesis, characterization and bioactivity of poly(DHP-*alt*-MA) and its derivatives, with different substituents (e.g., acetoxy, methoxy, ethoxy, methoxycarbonyl, formyl, acetoxymethyl, and tosyloxymethyl groups, as well as guanine derivatives) in the 2-position of pyran ring of the copolymer backbone. These pyran-containing copolymers with a high density of carboxylic acid functionality as the polynucleotide analogues exhibit antitumor activities in *in vitro*, which were found to have higher activities against the tumor cells (B16 and 3LL) than those of their acyclic analogues, especially alternating cyclocopolymer of divinyl ether with MA ( $M_n = 5500$  g/mol and  $M_w/M_n = 1.3$ ), whose biological activities have well been reported [2,10]. Radical-initiated binary and ternary polymerization of MA-DHP, DHP-MA-vinyl acetate (VA) and MA-DHP-N-isopropyl acrylamide acceptor-donor and donor-acceptor-donor monomer systems, respectively, also reported [11-13]. The synthesis and characterization of this copolymers, some kinetic parameters of reactions, the copolymer-thermal behavior relationship, and their antitumor activity were examined. The formation of charge-transfer complexes (CTC) in

the MA-donor monomer systems and complex-radical copolymerizations of MA with various electron-donor functional monomers such as *p*-dioxene [14], *p*-oxathiene [3], 2,3-dihydropyran [6], phenylvinyl alkyl ethers and thioethers [15], alkyl vinyl ethers [16] and 2-vinyl-1,3-dioxane [17] have been reported by many researchers. MA is an excellent monomer which can provide reactive anhydride or carboxylic groups, and amphiphilic molecules can be obtained easily via the copolymerization of MA and hydrophobic monomer. The basic concepts of complex-radical alternating copolymerization of maleic monomers were described by Rzaev [18]. Recently, extensive studies have been performed on the radical copolymerization of MA with other monomer and the self-assembly of their copolymers [19-27]. Blenkins [28] reported synthetic procedure for the alternating copolymers (oligomers with  $M_n$  1330 and 1790 g/mol) through radical copolymerization of 2,2-dimethyl- and 2-methyl-2-ethyl-4-vinyl-1,3-dioxolanes with maleic anhydride in toluene. According to this patent publication, the reactive anhydride groups in the copolymers can be utilized to crosslink the copolymers with a variety of materials to produce useful coatings, films, binders, and dispersing agents for particulate materials.

Biomaterials synthesized from synthetic polymers having biocompatible and bioactive properties have been developed for biomedical and tissue engineering applications [29-31]. Many researchers have investigated the degradable cyclic acetal biomedical polymers that produce less toxic degradation products, therefore decreasing the inflammatory response of the surrounding tissue [32-35]. Shi et al. [36] studied cyclic acetals that used as hydrogen donors for bimolecular photoinitiating systems and benzodioxole derivatives as a substitute for commercial aromatic tertiary amine in dental applications. Pate et al. [37] reported synthesis of the hydroxyapatite nanoparticle/cyclic acetal hydrogel systems to create nanocomposites that could be used to repair surgically created orbital floor defects in a rabbit animal model.

On the other hand, growing interest and much effort has been focused on the synthesis of boron-containing low molecular weight functional

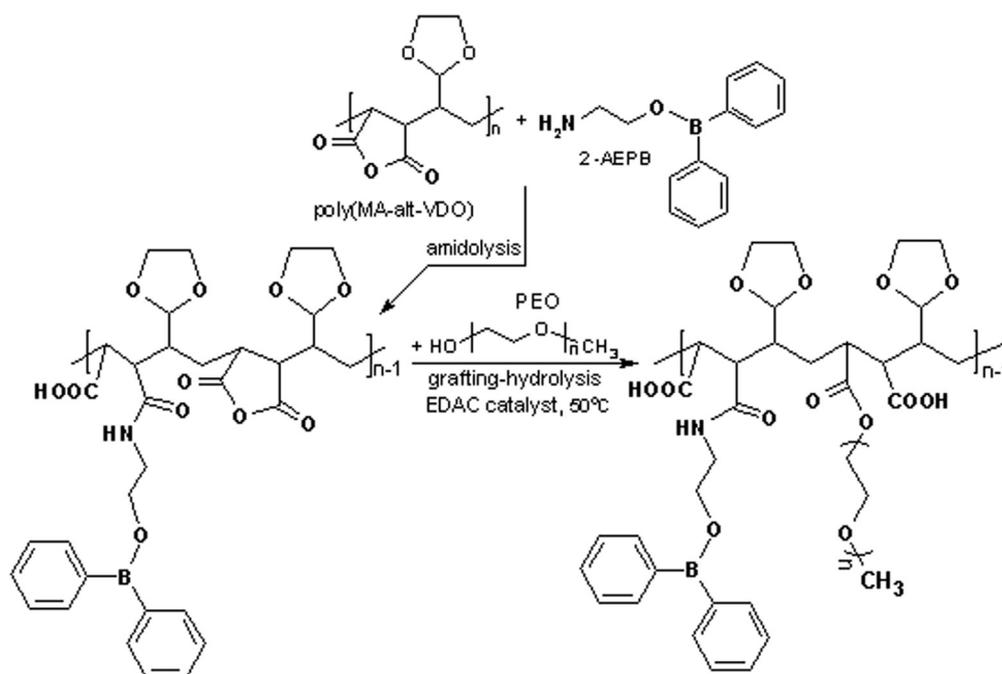

**Scheme 1.** Synthetic pathway of the organoboron amide-ester branched derivatives of alternating copolymer of maleic anhydride and 2-vinyl-1,3-dioxolane.

compounds, biopolymers and drugs with boron ligands and evaluation of their suitability for the bioengineering applications, especially for the Boron Neutron Capture Therapy (BNCT) [38,39]. Synthesis of novel organoboron functionalized copolymers and investigation of their interaction with various cancer cells were a subject of our recent publications [13,40,41]. However, synthesis of alternating copolymer of MA with 2-vinyl-1,3-dioxolane (VDO) as a cyclic analogue of methyl vinyl ether (antitumor activity of alternating copolymers of methyl vinyl (or divinyl) ethers with MA is well known [2]) by complex-radical bulk copolymerization and its organoboron and PEO functionalized derivatives as anticancer agents are not reported.

The goal of this work is synthesis and characterization of novel organoboron amide derivatives by amidolysis of poly(MA-*alt*-VDO) with 2-aminoethyldiphenyl borinate (2-AEPB) and their  $\alpha,\omega$ -hydroxyl-methoxy-poly(ethylene oxide) (PEO) macrobranches by grafting of synthesized organoboron copolymer with PEO to improve biocompatibility and degree of conjugation with biomacromolecules. An important aspect of this work is comparative investigations of the interactions of pristine alternating copolymer and its

organoboron and PEO branched derivatives with HeLa (human cervix carcinoma cell) cancer cells, and investigation of copolymer structure-composition-antitumor activity relationships. Synthetic pathway of the side-chain amide-ester-carboxyl functionalized organoboron copolymers can be represented as follows (Scheme 1).

## EXPERIMENTAL

### Materials

MA monomer (Fluka, Switzerland) was purified by recrystallization from anhydrous benzene solution and sublimation in vacuum. 2-Vinyl-1,3-dioxolane (VDO) was purchased from Aldrich: FTIR-ATR spectra ( $\text{cm}^{-1}$ ): 2994-2866 (m) antisym. Stretching C-H in  $\text{R-CH=CH}_2$ , 1437 (m) and 1347 (m)  $\text{CH}_2$  and C-H bending in  $\text{R-CH=CH}_2$ , respectively, 1147-1028 C-O vibration bands. 2-Aminoethyldiphenyl borinate (2-AEPB) (Sigma-Aldrich, Germany) was purified by recrystallization from anhydrous ethanol: m.p. 193.5°C (by DSC); FTIR-ATR spectra ( $\text{cm}^{-1}$ ): 3284 (vs) and 3220 (s) N-H stretching in  $\text{NH}_2$ , 3066-2870 (s) C-H stretching, C=C stretching in phenyl groups, 1491(m) and 1334 (m) B-O band, 1432 (vs) fairly strong, sharp band due to benzene ring vibration in phenyl-boronic acid linkage, 1263-1154 (s) fairly strong, sharp bands due to C-N stretching

in C-NH<sub>2</sub>, 1061 (vs) C-O bending and 750-710 (s) sharp bands from boron-phenyl linkage; <sup>1</sup>H NMR spectra (δ, ppm), in CHCl<sub>3</sub>-d<sub>1</sub>: CH<sub>2</sub>-O 1.49, CH<sub>2</sub>-NH<sub>2</sub> 2.96, and 7.38-7.40 (1H), 7.19-7.24 (2H) and 7.13-7.16 (2H) for protons of *p*-, *o*- and *m*-positions in benzene ring, respectively. α-Hydroxy-ω-methoxy-PEO (M<sub>n</sub> 2000 g.mol<sup>-1</sup>) (Fluka): <sup>1</sup>H NMR spectra (δ, ppm) in CHCl<sub>3</sub>-d<sub>1</sub>: CH<sub>2</sub>-O 3.75-3.45, OH end group 2.61 and O-CH<sub>3</sub> end group 2.16. α, α'-Azoisobutyronitrile (AIBN) (Fluka) as a initiator was purified by recrystallization from anhydrous ethanol. *N*-Ethyl-*N*-(3-dimethylaminopropyl) carbodiimide hydrochloride (EDAC) as a catalyst and folic acid (FA) as a targeting agent were supported from Aldrich-Sigma (Germany). All solvents and reagents were analytical grade and used without purification. HeLa (human cervix carcinoma cell) cancer cells were obtained from the tissue culture collection of the SAP Institute (Ankara, Turkey). Cell culture flasks and other plastic material were purchased from Corning (NY, USA). The growth medium, which is Dulbecco Modified Medium (DMEM) without L-glutamine supplemented fetal calf serum (FCS), Trypsin-EDTA were purchased from Biological Industries (Kibbutz Beit Haemek, Israel). The primary antibody, caspase-3 was purchased from Lab Vision (Germany), cell proliferation reagent WST (Roche, Germany).

### Synthesis of poly(maleic anhydride-*alt*-2-vinyl-1,3-dioxolane)

Poly(maleic anhydride-*alt*-2-vinyl-1,3-dioxolane) were synthesized by bulk polymerization technique. Appropriate quantities of solid MA were dissolved in liquid VDO with AIBN initiator under the nitrogen atmosphere. Reaction conditions: mole ratios of (VDO/MA) = 1:1 and AIBN = 1.0 wt.%. The reaction medium was mixed at 70°C for 6 h under a nitrogen atmosphere. Then, the synthesized copolymers were isolated from reaction mixture by precipitation with diethyl ether and dried at 60°C under vacuum. FTIR-ATR spectra (cm<sup>-1</sup>): 2962 (w) for backbone CH stretching band, 1781 (w) and 1724 (m) bands for antisymmetrical and symmetrical C=O band of MA unit, 1258 (w-m) and 1159 (m, broad) anhydride C-O-C stretching; <sup>1</sup>H NMR spectra (in DMSO-d<sub>6</sub> at 25°C) (δ, ppm): 1.38, 1.76 and 3.62 for the backbone CH, CH<sub>2</sub> (VDO unit) and CH-CH (MA unit), respectively, 3.92 and 6.5-6.1 for CH

and CH<sub>2</sub>-O of VDO ring, respectively and broad peak around 13.21-12.15 for partially hydrolyzed MA unit (-COOH); <sup>13</sup>C NMR spectra (δ, ppm): 66.2, 62.3-64.1 and 58.2 for the backbone carbon atoms in CH, CH<sub>2</sub> (VDO unit) and CH-CH (MA unit), respectively, 109 and around 60-58 for OCO and O-CH<sub>2</sub> of dioxolane ring, respectively, 167-164 for anhydride C=O group.

### Synthesis of 2-amidoethyldiphenylborinate-poly(MA-*alt*-VDO)

Amidolysis of poly(MA-*alt*-VDO) with 2-AEPB using various [copolymer]/[2-AEPB] molar ratios was carried out in *N,N'*-dimethylformamide (DMF) at 60°C with EDAC catalyst under a nitrogen atmosphere using a standard Pyrex-glass reactor supplied by a mixer, temperature control unit and condenser. Reaction conditions: [2-AEPB] = 0.066 mol.L<sup>-1</sup>, mole ratios of [(MA-co-VDO)/[2-AEPB] = 1:1, 3:1, 5:1 and EDAC = 1.0 wt.%. Appropriate quantities of poly(MA-co-VDO), 2-AEPB, DMF and EDAC were placed in a reactor and the reaction mixture was flushed with dried nitrogen gas for at least 2 min, then sealed and placed in a thermo stated silicon oil bath at 60°C to intensive mixing for 5 h. The organoboron amide copolymer was isolated from reaction mixture by precipitation with diethyl ether and dried under vacuum. FTIR-ATR spectra (KBr pellet), cm<sup>-1</sup>: 1734 (vs) C=O stretching (amide I band), 1651 (m) and 1558 (m, broad) N-H deformation (amide II band), 1437(w) and 1369 (m) C-N stretching (amide III band); <sup>1</sup>H NMR spectra (in DMSO-d<sub>6</sub> at 25°C), δ ppm: protons of phenyl groups 7.2-7.7, weak 2H from CH<sub>2</sub> in -CH<sub>2</sub>-CO-NH- fragment 5.9, very weak 2H from B-O-CH<sub>2</sub> group 3.25, 2H from NH-CH<sub>2</sub> 2.75 and 2H from backbone -CH-CH- group around 3.60-3.53; <sup>13</sup>C NMR spectra (δ, ppm): C=O of amide and carboxylic groups 165, CH= in phenyl groups around 135-127 (CH=), 163 (C-B), backbone CH<sub>2</sub> 17.1 and CH 10.2, CH<sub>2</sub>-O 36.5-32.3 (organoboron linkage), CH-CH 41-42, CH<sub>2</sub>-O and CH-O around 65-58 (dioxolane ring).

### Synthesis of 2-amidoethyldiphenylborinate-PEO-ester-poly(MA-*alt*-VDO)

The esterification (grafting) of organoboron amide polymer, containing 19.24 mol % of organoboron linkages, with PEO (M<sub>n</sub> 2000 g.mol<sup>-1</sup>) at polymer/PEO feed molar ratio 1:0.01 was carried out in DMF at 60°C for 1 h. PEO branched copolymer was

isolated from reaction mixture by precipitation with diethyl ether and dried 40°C under vacuum. Prepared PEO ester of organoboron copolymer has the following average characteristics: Boron (B) content 0.86 % (by ICP-MS) and 0.92 % (by TGA), and  $T_g$  146.8°C (by DSC);  $^1\text{H}$  NMR spectra (in  $\text{DMSO-d}_6$  at 25°C),  $\delta$  ppm: protons of CH-CH backbone around 4.15-3.92 for maleamide group,  $\text{CH}_2\text{-O}$  and  $\text{CH-O}$  of dioxolane ring around 4.65-4.58,  $\text{CH}_2\text{-O}$  and  $\text{CH}_3\text{-O}$  (end group) of PEO branch around 4.42-4.18 and 2.94, respectively, phenyl groups 7.92-7.70 (CH=) and 5.86 HN-CO amide group for organoboron linkage;  $^{13}\text{C}$  NMR spectra (d, ppm): 42.2 and 163 backbone CH-CH and C=O of maleamide unit, around 70-65 for  $\text{CH}_2\text{-O}$  and  $\text{CH-O}$  groups in dioxolane ring, 62 and 58  $\text{CH}_2\text{-O}$ , 52  $\text{CH}_3\text{-O}$  (end group) in PEO branch, around 136-127 CH= and 162.9 (C-B) in phenyl groups, 36.8 and 32.2  $\text{CH}_2$  of organoboron linkage.

### Characterization

Fourier transform infrared (FTIR-ATR) spectra were recorded with FTIR Nicolet 8700 spectrometer in the 3700-600  $\text{cm}^{-1}$  range.  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra were performed on a Bruker Avance (300 MHz) spectrometer with  $\text{DMSO-d}_6$  as a solvent at 25°C. Thermogravimetric (TGA) and differential scanning calorimetric (DSC) analyses were performed in a TGA-DTA (Perkin Elmer TG/DTA6300) and a DSC2010 Thermal Analyzers, respectively, under nitrogen atmosphere at a heating rate of 10°C/min. Boron amount in organoboron copolymers and PEO branched derivative were determined by TGA and High Resolution Inductively Coupled Plasma Mass Spectrometry (HR-ICP-MS) (Thermo Element XR)

with microwave digestion technique, respectively. WST assay for cytotoxicity, HeLa cells ( $5 \times 10^3$  cells per well) were placed in DMEM by using 96-well plates. The plates were kept in the  $\text{CO}_2$  incubator (37 °C in 5%  $\text{CO}_2$ ) for 72 h; the medium was replaced with fresh medium. Then, Different amounts of Copolymer (C), C-B, C-B-PEO (about 0-200  $\mu\text{g.mL}^{-1}$  in medium) were put into wells containing cells, respectively, and incubated at the same conditions for 72 h. Following of this incubation, WST reagent (15 $\mu\text{l}$ ) was added into each well, and the cells were cultured for further 4h incubation. After that, plates were read in Elisa Microplate Reader at 440 nm and reference wave length at 630 nm.

## RESULTS AND DISCUSSION

### The monomer reactivity ratios


Both the MA and VDO monomers are not homopolymerize with free radical initiation and related to the electron-acceptor-electron-donor system which are form a charge-transfer complex (CTC) and easily undergo to alternating copolymerization. Experimental results were summarized in Table 1. The compositions of copolymers were calculated using acid number values (AN) (by alkali titration) for the copolymers prepared from the various monomer feed ratios in the lower conversion conditions (around 5.5-9.6 %) according to the following our equation:

$$m_1 = \frac{W_2 \cdot 100}{\frac{2M(\text{KOH})}{\text{AN}} - (W_1 - W_2)} \quad (1)$$

**Table 1.** Copolymer Compositions for the Various Monomer Feeds and  $^1\text{H}$  NMR Analysis; Results for MA/VDO Acceptor-Donor Monomer Mixtures at  $[\text{MA}] \ll [\text{VDO}]$  in  $\text{CHCl}_3\text{-d}_1$  solution at 35°C.

Monomer feed (mol %) [MA] (VDO)	Acid Number (mgKOH/g)	Copolymer composition (mol %)		[MA] (mol L <sup>-1</sup> )	[VDO] <sup>-1</sup> (L mol)	<sup>1</sup> H NMR analysis	
		$m_1$	$m_2$			$d_c^{\text{MA}}$ (ppm)	$D_{\text{obs}}$ ( $D_{\text{obs}}^{-1}$ ) (ppm) (ppm) <sup>-1</sup>
30		48.95					0.110
70	554	51.05		0.1	0.25	7.010	9.09
40		49.18					0.085
60	557	50.82		0.1	0.50	7.035	11.76
50		50.16					0.075
50	568	49.84		0.1	1.00	7.045	13.33
70		50.50					0.068
30	572	49.50		0.1	2.00	7.052	14.71

\* $\delta_c^{\text{MA}}$  = 7.12 ppm for the protons of free MA.

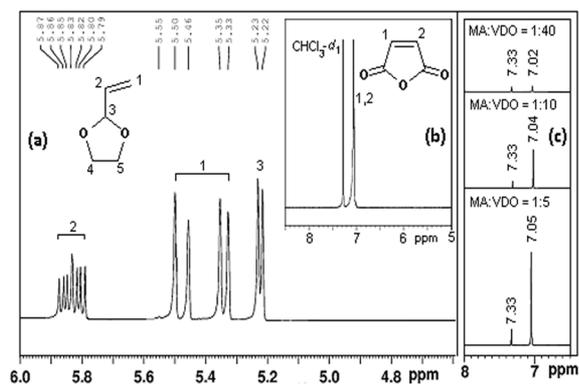

**Figure 1.**  $^1\text{H}$  NMR spectra of (a) vinyl-1,3-dioxolane, (b) maleic anhydride and (c) various MA/VDO monomer mixtures in  $\text{CHCl}_3\text{-}d_1$  at  $35^\circ\text{C}$ .

where  $W_1$  and  $W_2$  molecular weights of MA( $m_1$ ) and VDO ( $m_2$ ) monomer units (mol %), respectively. As seen from the monomer feed ratio-copolymer composition relationships, copolymerization of leads to the formation of copolymers of constant composition (close to a 1:1 molar one), irrespective of the composition of the monomer feed ratios. Since neither MA nor VDO homopolymerized under chosen binary copolymerization conditions, the monomer pair exhibits a strong tendency to alternating copolymerization ( $r_1, r_2 \ll 1$ ) according to known concept of 'homopolymerization' monomeric CTCs [18]. The formation of CTCs in this monomer system was verified by an analysis of the  $^1\text{H}$  NMR spectra of the pristine monomers and their various mixtures at  $[\text{VDO}] \gg [\text{MA}]$  (Figure 1), the results of which were also summarized in


Table 1. It can be seen from these Figures that the MA (acceptor) singlet has a high upfield shift ( $\Delta_{\text{obs}} = \delta_{\text{f}}^{\text{MA}} - \delta_{\text{obs}} = 7.12 - 7.01 = 0.11$  ppm for MA/VDO =1/40), while chemical shift of VDO (donor) double bond protons was almost not changed. The obtained values of chemical shifts ( $\Delta_{\text{obs}}$ ) allow us calculate the equilibrium constant ( $K_c = 0.029$  L.mol $^{-1}$  in  $\text{CHCl}_3\text{-}d_1$  at  $35^\circ\text{C}$ ) for MA...VDO complex from plots of  $[\text{VDO}]^{-1}$  (L mol $^{-1}$ ) versus ( $\Delta_{\text{obs}}^{-1}$ ) (ppm $^{-1}$ ) using the following known equation [42]:

$$[\text{VDO}]^{-1} = (\Delta_c K_c (\Delta_{\text{obs}})^{-1} - K_c) \quad (2)$$


where  $\Delta_{\text{obs}}$  is the difference in chemical shifts of free MA protons and those in MA/VDO mixtures at  $[\text{VDO}] \gg [\text{MA}]$ ;  $\Delta_{\text{obs}} = \delta_{\text{f}}^{\text{MA}}$  (chemical shift of free MA at 7.12 ppm) -  $\delta_{\text{c}}^{\text{MA}}$  (chemical shifts of complexed MA in the different MA/VDO monomer mixtures); ( $\Delta_{\text{obs}}^{-1}$ ) is the intercept on the ordinate axis and  $Tg\alpha = (\Delta_{\text{obs}})^{-1} K_c$ .

The monomer reactivity ratios ( $r_1$  and  $r_2$ ) of MA-VDO acceptor-donor monomer pair were calculated using obtained values of copolymer compositions (Table 1) and modified Kelen-Tüdös equation [43] from plot of  $(F^2/f)/(F^2/f + \alpha)$  versus  $F(f-1)/f + \alpha$ :  $r_1$  (MA) = 0.007 and  $r_2$  (VDO) = 0.002;  $r_1 K_c = 0.00026$  ( $\sim 0$ ) and  $r_2 K_c^{-1} = 0.054$ .


$$\frac{F(f-1)}{f} + \alpha = (r_1 K_c + \frac{r_2 K_c^{-1}}{\alpha}) (\frac{F^2}{f}) / (\frac{F^2}{f} + \alpha) \quad (3)$$

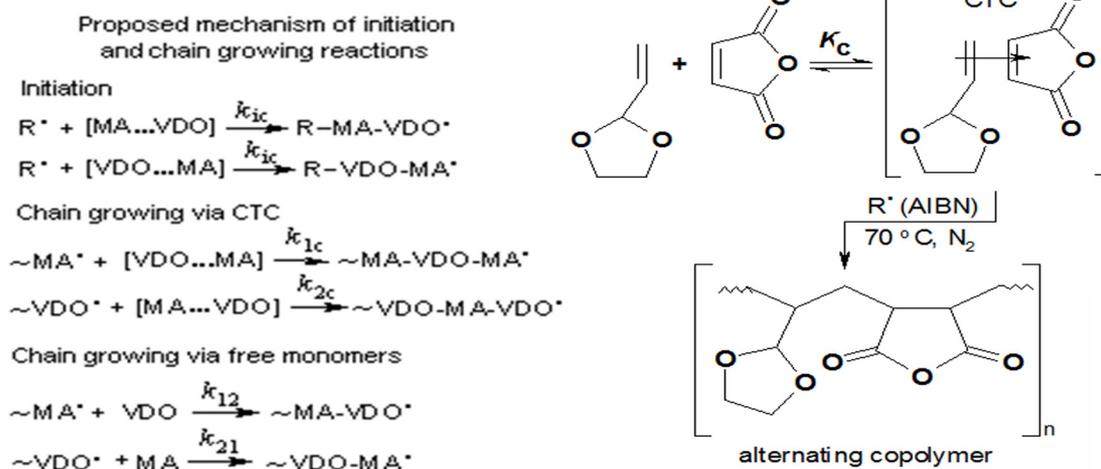

**Scheme 2.** Schematic representation of radical alternating copolymerization of MA (acceptor) and 2-vinyl-1,3-dioxolane (donor) via charge transfer complex formation and mechanism of initiation and chain growing reactions.

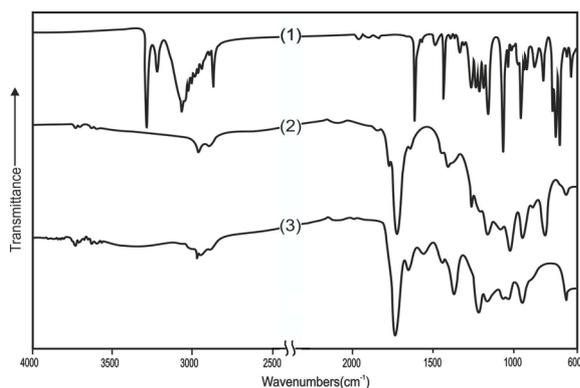

**Figure 2.** FTIR spectra of (1) 2-AEPB (2) poly(MA-co-VDO) and (3) poly(MA-co-VDO)-2-AEPB-1 organoboron copolymer.

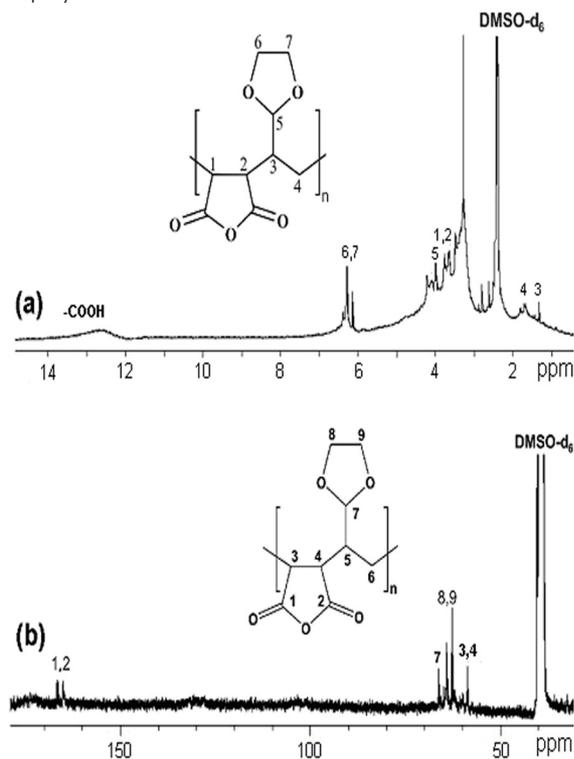

**Figure 3.** (a)  $^1\text{H}$  NMR and (b)  $^{13}\text{C}$  NMR spectra of poly(MA-alt-VDO) in  $\text{DMSO-d}_6$ .

where  $\alpha$  (arbitrary constant)  $\sim 1$ ,  $F = [\text{MA}]/[\text{VDO}]$  (monomer feed ratio) and  $f = m_1/m_2$  (monomer unit ratio in copolymer).


Thus, VDO monomer as cyclic analogue of alkyl vinyl ethers copolymerize with MA through formation CTC (1:1) and copolymer with strong alternating structure that reasonable agreement with classical theory of complex-radical alternating copolymerization of two non-homopolymerizable monomers [18]. Proposed mechanism of initiation and chain propagation reactions can be represented as follows (Scheme 2).

### Structure of Organoboron Derivatives of Poly(MA-alt-VDO)

The structures of synthesized copolymers, organoboron copolymers and their PEO branches were confirmed by FTIR-ATR and  $^1\text{H}$  ( $^{13}\text{C}$ ) NMR analysis. The characteristic C=C stretching bands of vinylenes and vinyl groups of MA and VDO monomers (around  $1631\text{-}1563\text{ cm}^{-1}$ ), respectively, are not observed in the FTIR-ATR spectra of copolymer (Figure 2). But, characteristic bands of anhydride and dioxalane units ( $1781$ ,  $1723$ ,  $1258$ , and  $1018\text{ cm}^{-1}$ ) are appeared in spectra of poly(MA-alt-VDO). Comparative spectral analysis of 2-AEPB, poly(MA-alt-VDO) and its organoboron derivative indicates that the characteristic bands of anhydride C=O groups disappearance in the spectra of poly(MA-alt-VDO)-B-1 polymer prepared from equimolar feed ratio of copolymer:2-AEPB = 1:1. The formation of amide group in this organoboron copolymer is confirmed by the appearance of new bands such as  $1734$  (amide I. band),  $1651$  and  $1558$  (amide II. band),  $1437$  and  $1369$  (amide III. band).

**Table 2.** Composition and Thermal Behavior of Alternating Copolymer and Its Organoboron Amide-Ester Derivatives.


Functional organoboron copolymers	B (%) (by TGA)	$T_g$ ( $^{\circ}\text{C}$ ) (by DSC)	$T_d$ ( $^{\circ}\text{C}$ ) (by TGA) first step degradation		
			$T_{d1}$	$T_{dmax}$	$T_{d2}$
Poly(MA-alt-VDO)	0.0	185.5	189	195	225
Poly(MA-alt-VDO)-g-B-1	3.69	142.0	152	170	231
Poly(MA-alt-VDO)-g-B-2	3.11	140.2	148	174	243
Poly(MA-alt-VDO)-g-B-3	1.85	135.5	151	178	255
Poly(MA-alt-VDO)-g-B-2-g-PEO	0.92	146.8	138	159	245

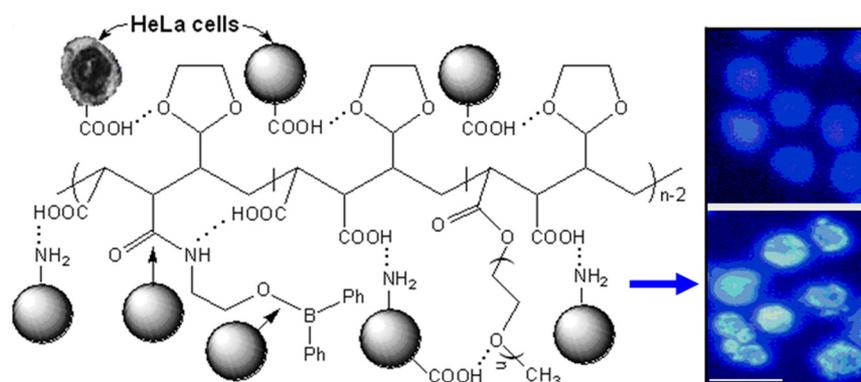


**Scheme 3.** Schematic representation of copolymer/HeLa cells conjugation. Images: before (from the top) and after (from the bottom) interaction. Scale: x400 magnification, 40  $\mu\text{m}$ . Inner ring structure of HeLa cell, which is presented in Scheme, was adapted from [44].

The characteristic proton peaks of VDO are observed  $\text{OCH}_2$  peaks at 4.7 ppm and 4.1 ppm in the  $^1\text{H}$  NMR spectra of poly(MA-*alt*-VDO) (Figure 3a). In the  $^{13}\text{C}$  NMR spectra of poly(MA-*alt*-VDO), characteristic carbon peaks of MA and VDO are also observed at 167-164 ppm for anhydride C=O, 109 ppm for OCO in dioxolane ring and 60-58 ppm for O- $\text{CH}_2$  in dioxolane ring, respectively (Figure 3b). Similar effect has been observed from comparative analysis of the  $^1\text{H}$  NMR and  $^{13}\text{C}$  NMR spectra of poly(MA-*alt*-VDO)-B-2 and its PEO branch poly(MA-*alt*-VDO)-B-PEO. The


results of this analysis are illustrated in Figures 4 and 5. The formation of H-bonded amide linkages is confirmed by a presence of characteristic peaks at 5.9 and 162 ppm in the  $^1\text{H}$  NMR and  $^{13}\text{C}$  NMR spectra of poly(MA-*co*-VDO)-B-2, respectively (Figure 4). In addition, the presence of characteristic proton peaks of organoboron linkages such as quarter phenyl peak at 7.2 ppm, triplet B-O- $\text{CH}_2$  peak at 3.25 ppm and quarter NH- $\text{CH}_2$  peak at 2.75 ppm (Figure 4a) also confirmed that 2-AEPB is covalently bound to anhydride units. In the  $^{13}\text{C}$  NMR spectra of poly(MA-

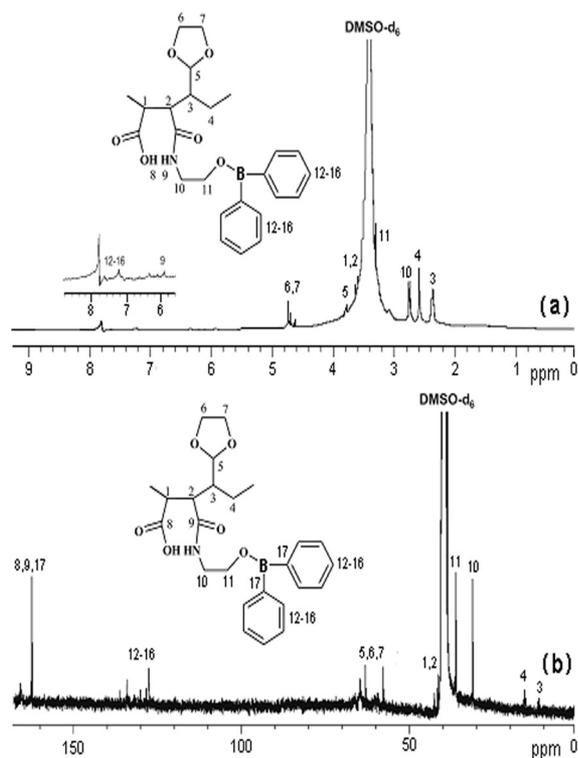

**Figure 4.** (a)  $^1\text{H}$  NMR and (b)  $^{13}\text{C}$  NMR spectra of poly(MA-*alt*-VDO)-g-AEPB-2 in  $\text{DMSO-d}_6$ .

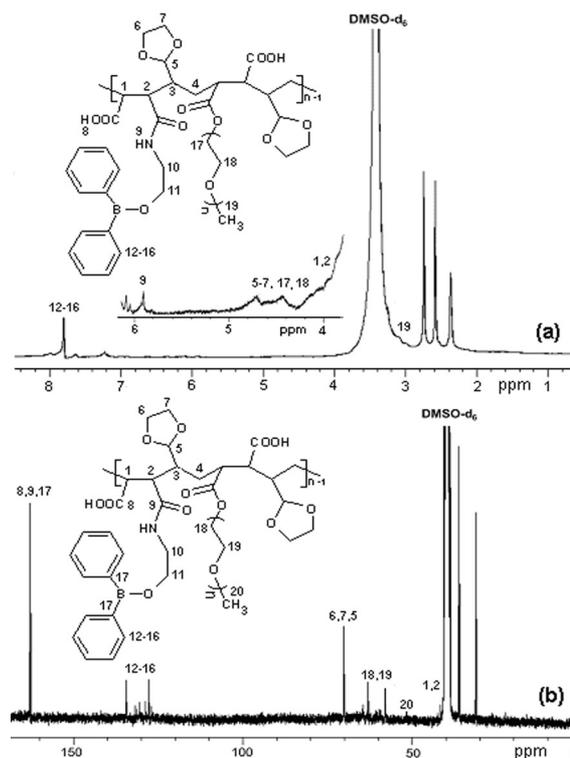

**Figure 5.** (a)  $^1\text{H}$  NMR and (b)  $^{13}\text{C}$  NMR spectra of poly(MA-*alt*-VDO)-g-AEPB-2-g-PEO in  $\text{DMSO-d}_6$ .

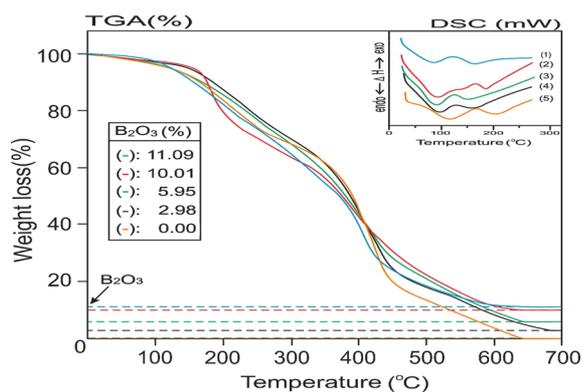


**Figure 6.** TGA and DSC curves of organoboron and PEO functionalized derivatives of copolymer: (1) poly(MA-*alt*-VDO)-*g*-2-AEPB-1, (2) poly(MA-*alt*-VDO)-*g*-2-AEPB-2, (3) poly(MA-*alt*-VDO)-*g*-2-AEPB-3, (4) poly(MA-*alt*-VDO)-*g*-2-AEPB-2-*g*-PEO and (5) pristine alternating copolymer. Heating rate 10°C/min under a nitrogen atmosphere.

co-VDO)-B-2 polymer (Figure 4b), the characteristic carbon resonances (163, 137-134, 66-63, 41, 42, 31 and 36 ppm) from organoboron fragment are also observed.  $^1\text{H}$  ( $^{13}\text{C}$ ) NMR spectra of PEO grafted organoboron copolymer [poly(MA-co-VDO)-B-PEO] were illustrated in Figure 5. The observed weak proton signals of side-chain PEO branches at 4.2 ppm for  $(\text{CH}_2\text{-CH}_2\text{-O})_n$  units and 3.25 ppm for  $\text{OCH}_3$  end group (Figure 5a) and carbon atom resonances (70 ppm for  $\text{O-CH}_2$  and 58 ppm for  $\text{OCH}_3$  end group) (Figure 5b) can be regarded as an additional fact to confirm the formation of side-chain macrobranched PEO linkages.

### Organoboron functional copolymer composition-property relationships

Thermal behavior and phase transitions of synthesized copolymers were investigated by differential scanning calorimetric (DSC) and thermal gravimetric analysis (TGA) methods. Last method also was utilized to determine the boron contents in organoboron copolymers. The obtained results were summarized in Figure 6. It was found that poly(MA-*alt*-VDO) and its organoboron and PEO branched derivatives exhibit amorphous structure with characteristic broad *endo*-peaks, which are associated with the glass-transition temperatures ( $T_g$ ), significantly depend on the composition and content of organoboron linkages in the functional copolymers. The higher values of  $T_g$  are observed for the polymers containing relatively high organoboron linkages. Therefore, rigid H-bonded structure provides high  $T_g$  in the organoboron copolymers (curves 1-3).

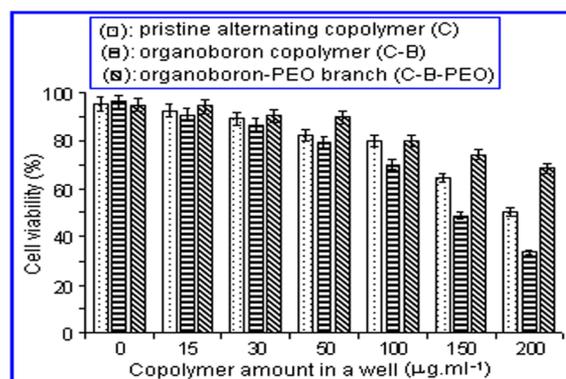

**Figure 7.** In vitro cytotoxicity of pristine alternating copolymer and its organoboron and PEO functionalized derivatives with different amount in a well at 72 h incubation. Results are presented as means  $\pm$  SEM.

For the copolymer poly(MA-*alt*-VDO) (curve 5), the relatively low values of  $T_g$  are observed. The results of TGA analyses (Figure 7) indicate that the organoboron and PEO branched derivatives of poly(MA-*alt*-VDO) show higher thermal stability which increases with increasing degree of grafted organoboron linkage in the copolymer. The observed two step degradation of the poly(MA-co-VDO) and its functionalized derivatives indicates occurrence of some macromolecular reactions such as anhydridization-decarboxylation reactions in the first step and main chain degradation in the second step. Relatively higher thermal stability was observed for PEO branched derivative of organoboron copolymer (Figure 7, curve 5). This fact can be explained by an additional effect of H-bonded PEO branches through ether...carboxyl ( $>\text{O}\dots\text{HOOC}$ -) interaction. TGA analyses also allow us to determine the content of boron in studied functionalized copolymers, results of which are summarized in Table 2.

### Cytotoxicity

The obtained cytotoxicity results of the pristine alternating copolymer (C) and its organoboron amide (C-B) and organoboron amide-ester (C-B-PEO) derivatives on cancer cells using a WST method were illustrated in Figure 7. As seen from plots of concentration of polymers versus percent of cell viability, the toxicity of pristine copolymer (C) against HeLa cells decreased with increasing in polymer concentration from 15 to 200  $\mu\text{g}\cdot\text{mL}^{-1}$  for 24 h incubation at 37°C. The toxicity of C-B was more significant than other copolymers. Figure 7

shows that the number of viable cells is above 70 % for HeLa cells after incubation of the cells with C-B at concentrations around 15-50  $\mu\text{g.mL}^{-1}$  for 24 h incubating time in cell culture media. The number of viable cells was lower than 50 % for HeLa in the range of 100-200  $\mu\text{g.mL}^{-1}$  concentration. When organoboron linkage was introduced to the structure of copolymer via amidization, the cytotoxicity was increased. However, the toxicity for HeLa cells significantly increases for organoboron copolymer concentrations above 100  $\mu\text{g.mL}^{-1}$ . When organoboron copolymer was modified with PEO (C-B-PEO), the cytotoxicity was decreased because of PEO biocompatibilization effect of PEO long branches. The cytotoxicity of PEO containing organoboron copolymer was lower than those without PEO in 15-200  $\mu\text{g.mL}^{-1}$  concentration. Viable cell ratio (%) was  $41.6 \pm 3\%$  (C),  $27.8 \pm 3\%$  (C-B) and  $60.4 \pm 3\%$  (C-B-PEO) for the pristine alternating copolymer and its organoboron amide-carboxyl and amide-ester-carboxyl derivatives, respectively. The possible interactions between functional copolymer and HeLa cells can be schematically represented as follows (Scheme 3.)

As seen from this scheme, the conjugation of copolymer with DNA biomacromolecules of HeLa cell through cells/ionized amide and organoboron groups ( $\rightarrow$ ),  $-\text{H}_2\text{N}\dots\text{HOOC}-$  and (ether)  $> \text{O}\dots\text{HOOC}-$  H-bondings can significantly influence the destruction process of supramacromolecular structure of HeLa cell biomacromolecules, and therefore, can be exhibited apoptotic and necrotic effects.

## CONCLUSIONS

Novel bioengineering alternating copolymer and its organoboron amide-ester-carboxyl functionalized copolymers were synthesized and characterized. This work presents the synthesis of novel poly(MA-*alt*-VDO) alternating copolymer and its organoboron, PEO branched derivatives by complex-radical copolymerization, amidization and grafting-esterification reactions, respectively. It was found that composition of copolymer is not dependent on the monomer feed ratios and

the VDO (donor) and MA (acceptor) monomers as non-homopolymerizable monomers exhibit strong tendency to the formation of charge-transfer complex ( $K_c = 0.021 \text{ L.mol}^{-1}$ ) and alternating copolymers ( $r_1(\text{MA}) = 0.007$  and  $r_2(\text{VDO}) = 0.002$ ). The synthesized organoboron and PEO functionalized copolymers contain a combination of ionizable groups (carboxylic, amide and organoboron groups), hydrophilic/hydrophobic and H-bonding fragments allow us utilize as amphiphilic bioengineering copolymers for evaluation of their antitumor activity (cytotoxicity). The functional copolymer structure-composition-property relationships and their cytotoxicity against HeLa cancer cells were investigated. It was demonstrated that the synthesized organoboron copolymers exhibit high antitumor activity through complex formation (H-bonding), and therefore, significantly influence the destruction process of supramacromolecular structure of HeLa cell biomacromolecules. Evaluation of the apoptotic and necrotic effects in the interaction of these multifunctional copolymers with HeLa cells using a combination of various biochemical and microscopy analysis methods will be a subject of our future investigations.

## ACKNOWLEDGEMENTS

The supports of this work by the TAEK (Turkish Atomic Energy Authority) and TÜBİTAK (Turkish Scientific and Technology Research Council) through TAEK-A3.H2.P2.01 and TBAG-2386 projects are gratefully acknowledged.

---

## R E F E R E N C E S

---

1. K. Ulbrich, T. Etrych, P. Chytil, M. Jelinkova, B. Rhova, J. Cont. Release, 87 (2003) 33.
2. GB. Butler, Cyclopolymerization and cyclocopolymerization, (1992). New York, Marcel Dekker.
3. S. Iwatsuki, Y. Yamashita, The charge transfer complex formation between p-dioxene and maleic anhydride and their participation in polymerization, Makromol. Chem., 89 (1965) 205.

4. T. Kokubo, S. Iwatsuki, Y. Tamashita, Studies on the charge-transfer complex and polymerization. XVII. The reactivity of the charge-transfer complex in alternating radical copolymerization of vinyl ethers and maleic anhydride, *Macromol.*, 1 (1968) 482.
5. T. Kokubo, S. Iwatsuki, Y. Tamashita, Studies on the charge-transfer complex and polymerizations, Part XIX. Spontaneous copolymerization of 1,2-dimethoxyethylen and p-dioxene with maleic anhydride, *Makromol. Chem.*, 123 (1969) 256.
6. K. Fujimori, Copolymerization of 2,3-dihydropyran and ethyl vinyl ether with maleic anhydride, *J. Macromol. Sci.-Chem A*, 9 (1975) 495.
7. Z.M. Rzaev, L.V. Bryksina, S.I. Sadikh-zade, Charge Transfer Complexes of maleic anhydride in radical homo-and copolymerization, *J. Polym. Sci. Part 1: Symp.*, 42 (1973) 519.
8. M.J. Han, K.H. Kim, T.J. Cho, K.B. Choi, Synthesis and characterization of poly[(3,4-dihydro-2H-pyran)-alt-(maleic anhydride)] and its derivatives: Biologically active polymers, *J. Polym. Sci. Part A: Polym. Chem.*, 28 (1990) 2719.
9. M.J. Han, K.S. Kim, T.J. Cho, K.H. Kim, J.Y. Chang, Polyribonucleotide Analogs: Synthesis and Physicochemical Properties, *Macromolecules*, 27 (1994) 2896.
10. I.G. Donaruma, Anionic polymeric drugs, (1980), New York, Wiley.
11. H.K. Can, A.L. Doğan, Z.M.O. Rzaev, A.H. Üner, A. Güner, Synthesis and antitumor activity of poly(3,4-dihydro-2H-pyran-co-maleic anhydride-co-vinyl-acetate), *J. Appl. Polym. Sci.*, 96 (2005) 2352.
12. Z.M.O. Rzaev, M. Türk, A. Uzgören, Bioengineering functional copolymers. XV. Synthesis and characterization of poly(N-isopropyl acrylamide-co-3,4-dihydro-2H-pyran-alt-maleic anhydride)s and their PEO branched derivatives, *J. Polym. Sci. Part A: Polym. Chem.*, 48 (2010) 4285.
13. M. Türk, Z.M.O. Rzaev, S.A. Khalilova, Bioengineering functional copolymers. XIV. Synthesis and interaction of poly(isopropyl acrylamide-co-2,3-dihydro-2H-pyran-alt-maleic anhydride)s with SCLC cancer cells, *Bioorg. Med. Chem.*, 18 (2010) 7975.
14. Y.K. Han, S.K. Choi, Synthesis and polymerization of 8,9-benzo-2-methylene-1,4,6-trioxaspiro[4,4]nonane (BMTN), *J. Polym. Sci. Polym. Chem. Ed.*, 21 (1983) 353.
15. T. Otsu, H. Inoue, Alternative copolymerization of vinyl sulfides with maleic anhydride, III. Alternative copolymerization, *Makromol. Chem.*, 128 (1969) 31.
16. K. Fujimori, A. Wickramasinghe, The reactivity of the charge-transfer complex of butyl vinyl ether and maleic anhydride in the radical terpolymerization of butyl vinyl ether, *Austral. J. Chem.*, 33 (1980) 189.
17. A.I. Smirnov, G.I. Deryabina, A.B. Kalabina, T.L. Petrova, I.L. Stoyachenko, V.B. Golubev, V.P. Zubov, Investigation of alternating copolymerization mechanism of vinyl ethers with derivatives of maleic acid, *Vysokomol. Soyed. A.*, 20 (1978) 1794.
18. Z.M.O. Rzaev, Complex-radical alternating copolymerization, *Prog. Polym. Sci.*, 25 (2000) 163.
19. L.M. Croll, H.D.H. Stover, Mechanism of self-assembly and rupture of crosslinked microspheres and microgels at the oil-water interface, *Langmuir*, 19 (2003) 10077.
20. M.Q. Zhu, L.H. Wei, M. Li, L. Jiang, F.S. Du, Z.C. Li, A unique synthesis of a well-defined block copolymer having alternating segments constituted by maleic anhydride and styrene and the self-assembly aggregating behavior thereof, *Chem. Commun.* 4 (2001) 365.
21. M.C. Davies, J.V. Dawkins, D.J. Hourston, Radical copolymerization of maleic anhydride and substituted styrenes by reversible addition-fragmentation chain transfer (RAFT) polymerization, *Polymer*, 46 (2005) 1739.
22. G. Kahraman, O. Beskardes, Z.M.O. Rzaev, E. Piskin, Bioengineering polyfunctional copolymers. VII. Synthesis and characterization of copolymers of p-vinylphenyl boronic acid with maleic and citraconic anhydrides and their self-assembled macrobranched supramolecular architectures, *Polymer* 45 (2004) 5813
23. E. Chernikova, P. Terpugova, C. Bui, B. Charleux, Effect of comonomer composition on the controlled free-radical copolymerization of styrene and maleic anhydride by reversible addition-fragmentation chain transfer (RAFT), *Polymer*, 44 (2003) 4101.
24. H. Kesim, Z.M.O. Rzaev, S. Dinçer, E. Piskin, Functional bioengineering copolymers. I. Synthesis and characterization of amphiphilic poly(N-isopropylacrylamide-co-maleic anhydride) and its macrobranched derivatives, *Polymer*, 44 (2003) 2897.
25. M.C. Davies, J.V. Dawkins, D.J. Hourston, E. Meehan, Molar mass determination of poly(octadecene-alt-maleic anhydride) copolymers by size exclusion chromatography and dilute solution viscometry, *Polymer*, 43 (2002) 4311.
26. J. Zhou, L. Wang, C. Wang, T. Chen, H. Yu, Q. Yang, Synthesis and self-assembly of amphiphilic maleic anhydride-stearyl methacrylate copolymer, *Polymer*, 46 (2005) 11157.
27. F. Delie, M.J. Blanco-Prieto, Polymeric particulates to improve oral bioavailability of peptide drugs. *Molecules*, 10 (2005) 65.
28. R.W. Blevins (Eastman Chem. Co., USA), Copolymers of dioxolanes and maleic anhydride, *Eur. Pat.* 0522046 B1 (1991).

29. A.S. Hoffman, Polymeric particulates to improve oral bioavailability of peptide drugs, *Artif. Organs*, 19 (1995) 458.
30. I.Y. Galaev, B. Mattiasson, 'Smart' polymers and what they could do in biotechnology and medicine, *Trends Biotechnol.*, 17 (1999) 335.
31. J.L. Moreau, D. Kesselman, J. Fisher, Synthesis and properties of cyclic acetal biomaterials, *J. Biomed. Mater. Res. A*, 81 (2007) 594.
32. M.W. Betz, P.C. Modi, J.F. Caccamese, D.P. Coletti, J.J. Sauk, J.P. Fisher, Cyclic acetal hydrogel system for bone marrow stromal cell encapsulation and osteodifferentiation, *J. Biomed. Mater. Res. A.*, 86 (2008) 662.
33. S. Kaihara, S. Matsumura, J.P. Fisher, Synthesis and characterization of cyclic acetal based degradable hydrogels, *EU J. Pharm. Biopharm.*, 68 (2008) 67.
34. N.A. Petasis, Expanding roles for organoboron compounds—versatile and valuable molecules for sythetic, biological and medicinal chemistry, *Aust. J. Chem.*, 60 (2007) 795.
35. W. Yang, X. Gao, B. Wang, Boronic acid compounds as potential pharmaceutical agents, *Med. Res. Rev.*, 23 (2003) 346.
36. S. Shi, H. Gao, G. Wu, J. Nie, Cyclic acetal as coinitiator for bimolecular photoinitiating systems, *Polymer*, 48 (2007) 2860.
37. M. Patel, M.W. Betz, E. Geibel, K.J. Pateş, J.F. Caccamese, D.P. Coletti, J.J. Sauk, J.P. Fisher, Cyclic acetal hydroxyapatite nanocomposites for orbital bone regeneration, *Tissue Eng Part A.*, 16 (2010) 55.
38. J.F. Valliant, K.J. Guenther, A.S. King, P. Morel, P. Schaffer, O.O. Sogbein, K.A. Stephenson, The medical chemistry of carborones, *Coord. Chem. Rev.*, 232 (2002) 173.
39. W. Chen, S.C. Mehta, D.R. Lu, Selective boron drug delivery to brain tumor for boron neutron capture therapy, *Adv. Drug. Deliv. Rev.*, 26 (1997) 231.
40. Z.M.O. Rzayev, M. Türk, G. Kahraman, E. Pişkin, Bioengineering functional copolymers, XIX. Synthesis of anhydride-organoboron functionalized copolymers and their interaction with cancer cells, *Hacettepe J. Biol. & Chem.*, 39 (2011) 111.
41. M. Türk, G. Kahraman, S.A. Khalilova, Z.M.O. Rzayev, S. Oğuztüzün, Bioengineering functional copolymers. XVII. Interaction of organoboron amide-ester branched derivatives of poly(acrylic acid) with cancer cells, *J. Cancer Therapy*, 2 (2011) 266.
42. M.W. Hanna, A.L. Ashbauch, Nuclear magnetic resonance study of molecular complexes of 7, 7, 8, 8-tetracyanoquinodimethane and aromatic donors, *J. Phys. Chem.* 68 (1964) 81.
43. T. Kelen, F. Tüdös, Analysis of the linear methods for determining copolymerization reactivity ratios. I. A new improved linear graphic method, *J. Macromol. Sci. Part A: Chem.* 9 (1975) 1.
44. P. Comes, W.W. Franke, Composition, structure and function of HeLa cell nuclear envelope, I. Structural data, *Z. Zellforsch.*, 107 (1970) 240.